



**HAL**  
open science

# Metal-Organic Framework vs. Coordination Polymer-Influence of the Lanthanide on the Nature of the Heteroleptic Anilate/Terephthalate 3D Network

Mariangela Oggianu, Fabio Manna, Suchithra Ashoka Sahadevan, Narcis Avarvari, Alexandre Abhervé, Maria Laura Mercuri

► **To cite this version:**

Mariangela Oggianu, Fabio Manna, Suchithra Ashoka Sahadevan, Narcis Avarvari, Alexandre Abhervé, et al.. Metal-Organic Framework vs. Coordination Polymer-Influence of the Lanthanide on the Nature of the Heteroleptic Anilate/Terephthalate 3D Network. *Crystals*, 2022, 12 (6), pp.763. 10.3390/cryst12060763 . hal-03855114

**HAL Id: hal-03855114**

**<https://univ-angers.hal.science/hal-03855114v1>**

Submitted on 16 Nov 2022

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution 4.0 International License

1 Article

# 2 Metal-Organic Framework vs Coordination Polymer - Influence 3 of the Lanthanide on the Nature of the Heteroleptic Anil- 4 ate/Terephthalate 3D Network

5 Mariangela Oggianu <sup>1,2</sup>, Fabio Manna <sup>1,3</sup>, Suchithra Ashoka Sahadevan <sup>1,3</sup>, Narcis Avarvari <sup>3</sup>, Alexandre Abhervé <sup>3,\*</sup>  
6 and Maria Laura Mercuri <sup>1,2\*</sup>

7 <sup>1</sup> Dipartimento di Scienze Chimiche e Geologiche, Università degli Studi di Cagliari, I-0942 Monserrato, Ca-  
8 gliari, Italy

9 <sup>2</sup> INSTM, Cagliari Unit, Via Giuseppe Giusti, 9, 50121 Firenze, Italy

10 <sup>3</sup> Univ Angers, CNRS, MOLTECH-Anjou, SFR MATRIX, F-49000 Angers, France

11 \* Correspondence: alexandre.abherve@univ-angers.fr (A.A.); mercuri@unica.it (M.L.M.)

12 **Abstract:** Metal-organic frameworks (MOFs), whose definition was regularly debated, are a  
13 sub-class of coordination polymers (CPs) which may feature both an overall 3D architecture and  
14 some degree of porosity. In this context, MOFs based on lanthanides (Ln-MOFs) could find many  
15 applications due to the combination of sorption properties and magnetic/luminescent behaviours.  
16 Here we report rare examples of 3D Ln-CPs based on anilate linkers, obtained under solvothermal  
17 conditions using a heteroleptic strategy. The three compounds of formula  
18  $[\text{Yb}_2(\mu\text{-ClCNAn})_2(\mu\text{-F}_4\text{BDC})(\text{H}_2\text{O})_4](\text{H}_2\text{O})_3$  (**1**),  $[\text{Er}_2(\mu\text{-ClCNAn})_2(\mu\text{-F}_4\text{BDC})(\text{H}_2\text{O})_4](\text{H}_2\text{O})_4$  (**2**)  
19 and  $[\text{Eu}_2(\mu\text{-ClCNAn})_2(\mu\text{-F}_4\text{BDC})(\text{H}_2\text{O})_4]$  (**3**) have been characterized by single-crystal X-ray dif-  
20 fraction, thermogravimetric analysis and optical measurements. Structural characterization re-  
21 vealed that compounds **1** and **2** present an interesting MOF architecture with extended rectangular  
22 cavities which are only filled with water molecules. On the other hand, compound **3** shows a much  
23 more complex topology with no apparent cavities. We discuss here the origins of such differences  
24 and highlight the crucial role of the Ln(III) ion nature for the topology of the CP. Compounds **1** and  
25 **2** now offer a playground to investigate the possible synergy between gas/solvent sorption and  
26 magnetic/luminescent properties of Ln-MOFs.

Citation: Lastname, F.; Lastname, F.;  
Lastname, F. Title. *Crystals* **2022**, *12*, 27  
x. <https://doi.org/10.3390/xxxxx> 28

**Keywords:** metal-organic framework; lanthanides; chlorocyananilate; tetrafluoroterephthalate

Academic Editor: Firstname Last-  
name

Received: date 29

Accepted: date 30

Published: date 31

32

**Publisher's Note:** MDPI stays  
neutral with regard to jurisdictional  
claims in published maps and  
institutional affiliations. 33  
34  
35  
36



**Copyright:** © 2022 by the author 37  
38

Submitted for possible open access 39

publication under the terms and 40

conditions of the Creative Commons 41

Attribution (CC BY) license 42

([https://creativecommons.org/licenses](https://creativecommons.org/licenses/by/4.0/) 43

[https://creativecommons.org/licenses](https://creativecommons.org/licenses/by/4.0/) 44


## 29 1. Introduction

30 Coordination polymers (CPs) and metal-organic frameworks (MOFs) are important  
31 classes of molecular materials in solid-state and coordination chemistry. However, if the  
32 prime definition of a CP was the non-molecular assembly of metal centres through or-  
33 ganic linkers by covalent and/or ionic bonds, the CPs/MOFs terminology remained  
34 confusing for decades [1]. Even though it was widely accepted that MOFs are a sub-class  
35 of CPs [2], the discrimination criteria for MOFs was unclear. From the survey proposed  
36 by Öhrström *et al.* about the definition of a MOF (mostly described as “a network with  
37 frames”) [1] as well as the definition given by James (structures “which exhibit porosity”)  
38 [3], and based on MOFs properties that are often associated with gas sorption, it seems  
39 now approved that a MOF should exhibit a 3D structure with some degree of porosity.  
40 Among them, CPs or MOFs based on rare earth metals, especially lanthanide(III) ions  
41 (hereafter called Ln-CPs or Ln-MOFs), were especially investigated for magnetic [4]  
42 and/or luminescence properties [5-7], but also adsorption [8], sensing properties [9-10]  
43 and more recently circularly polarized luminescence [11]. The more flexible coordination  
44 numbers and geometries of Ln(III) ions compared to transition metal ions make the pre-

Mis en forme : Anglais (États  
Unis)

Mis en forme : Anglais (États  
Unis)

45 diction of Ln-CPs architectures challenging. Crystal structures topologies and dimen-  
46 sionalities can indeed be affected by the synthetic conditions, the presence of coordinated  
47 solvent molecules [12] and the choice of the organic linker [13], but also by the nature of  
48 the Ln(III) ion [14]. Most of the ligands used are carboxylates derivatives due to their  
49 hard base behaviour [2]. Among them, oxalate [15], succinate [16] and some other ali-  
50 phatic linkers were used [17], but most of the reported examples contain aromatic linkers  
51 such as squarate [18-19], 1,4-benzene-dicarboxylate (usually called terephthalate) [20],  
52 1,3,5-benzene-tricarboxylate [21] or more extended  $\pi$ -conjugated linkers [22-23], and  
53 more recently imidazole [24-26], pyridine [27] or pyrimidine-based bridging ligands [28].  
54 Alternatively, derivatives of 2,5-dihydroxy-1,4-benzoquinone, usually called anilates,  
55 have been extensively used in the last decade to prepare CPs with either transition metal  
56 ions [29-30] or lanthanides [31]. The choice of the anilate linker could afford interesting  
57 magnetic properties due to the presence of magnetic exchange interactions through the  
58 bis-bidentate ligand and the redox ability of the anilate. On the other hand, the good an-  
59 tenna effect of the anilate linkers has shown to be efficient especially for near-infrared  
60 (NIR) emitting Ln(III) ions [32]. Most examples of Ln(III)-anilate compounds previously  
61 reported are 2D coordination polymers [33]. Indeed, while several examples of 3D coordi-  
62 nation polymers based on transition metal ions and anilate linkers have been reported  
63 [34-36], only three publications have described 3D Ln(III)-anilate compounds [37-39].  
64 However in 2D CPs, the structural versatility was already observed depending either on  
65 the nature of the Ln(III) ion or the choice of the solvent, ranging from (4,3) topology with  
66 square cavities to (6,3) topology with either strongly distorted rectangular cavities or  
67 more regular hexagonal cavities [40]. In order to promote higher dimensionalities of the  
68 extended network, one strategy consists in using multiple linkers and thus create addi-  
69 tional connections between metal centres. A representative example was reported by  
70 Wang et al. with the 3D CP of formula  $[\text{Ln}(\text{tpbz})(\text{tdc})]$  (Ln = Sm, Eu, Tb) obtained by the  
71 use of both 4-(2,2':6',2''-terpyridin-4'-yl)benzoate (tpbz) and 2,5-thiophenedicarboxylate  
72 (tdc) [13]. One less conventional example was reported by the team of Wu, where hy-  
73 drolysis of DMF could induce the formation of formate (fa) ligands followed by the  
74 crystallization of Ln-CPs of formula  $[\text{Ln}(\text{tpa})(\text{fa})]$  (Ln = Eu, Gd, Tb; tpa = terephthalate). In  
75 these series of compounds, 2D Ln-formate layers were further connected by tpa linkers to  
76 form an overall 3D network [41]. As part of our research endeavour on anilate Ln-CPs,  
77 we applied herein the multiple linkers strategy, hereafter called heteroleptic strategy, in  
78 order to afford 3D Ln-CPs based on the anilate ligands. We thus selected the  
79 3-chloro-6-cyano-2,5-dihydroxy-1,4-benzoquinone (chlorocyananilate,  $\text{ClCNAn}^{2-}$ ) and  
80 2,3,5,6-tetrafluoroterephthalate ( $\text{F}_4\text{BDC}^{2-}$ ) [42-43] bridging ligands since the use of these  
81 two linkers already allowed some of us to obtain heteroleptic 2D Ln-CPs [44-45]. In this  
82 work, we have been able to crystallize in a highly reproducible manner, under sol-  
83 vothermal conditions, the 3D compounds of formula  
84  $[\text{Yb}_2(\mu\text{-ClCNAn})_2(\mu\text{-F}_4\text{BDC})(\text{H}_2\text{O})_4]\cdot(\text{H}_2\text{O})_3$  (1),  
85  $[\text{Er}_2(\mu\text{-ClCNAn})_2(\mu\text{-F}_4\text{BDC})(\text{H}_2\text{O})_4]\cdot(\text{H}_2\text{O})_4$  (2) and  $[\text{Eu}_2(\mu\text{-ClCNAn})_2(\mu\text{-F}_4\text{BDC})(\text{H}_2\text{O})_6]$   
86 (3). Crystal structures determinations reveal that in compounds 1 and 2 the 3D network is  
87 made by six-membered rings with regular rectangular shape and presence of large ex-  
88 tended cavities, therefore 1 and 2 can be described as Ln-MOFs, while compound 3 pre-  
89 sents a dense and more complex architecture with no apparent voids, highlighting the  
90 influence of the Ln(III) on the nature of the Ln-CP.

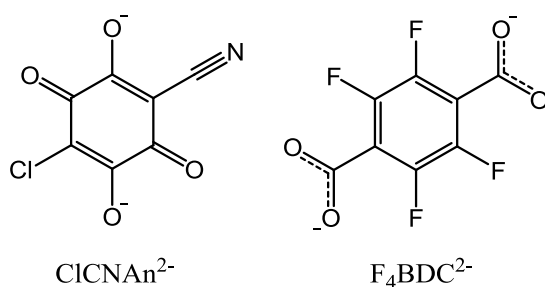

**Chart 1.** Structures of the bridging ligands used in this work.

## 2. Materials and Methods

### 2.1. Materials

Reagents were purchased from Zentek (TCI) and used without further purification. KHClCNA was synthesized as previously reported [46].

### 2.2. Synthesis

Compounds **1**, **2** and **3** were synthesized *via* hydrothermal approach. A 80 mL Teflon-lined stainless-steel autoclave reactor with a mixture of Ln(NO<sub>3</sub>)<sub>3</sub>·xH<sub>2</sub>O (Ln<sup>III</sup>= Yb<sup>III</sup>, Er<sup>III</sup> and Eu<sup>III</sup>) (0,3 mmol), KHClCNA (0,15 mmol), H<sub>2</sub>F<sub>4</sub>BDC (0,15 mmol), NaOH (0,45 mmol) and water (40 mL) was heated at 100 °C for 48h. After cooling to room temperature, red crystals suitable for X-ray diffraction analysis were obtained.

### 2.3. X-ray Crystallography

Single crystals of compounds **1**, **2** and **3** were mounted on glass fiber loops using a viscous hydrocarbon oil to coat the crystal and then transferred directly to the cold nitrogen stream. Data collection were performed on an Agilent Supernova with Cu-K<sub>α</sub> (λ = 1.54184 Å). The structures were solved by direct methods with the SIR97 program and refined all F<sup>2</sup> values with the SHELXL-2016/4 program using the WinGX graphical user interface. All non-hydrogen atoms were refined anisotropically. All hydrogen atoms were placed in calculated positions and refined isotropically with a riding model. A summary of the crystallographic data and the structure refinement is given in Table S1. CCDC 2170833-2170835 contain the supplementary crystallographic data for the paper. These data can be obtained free of charge from The Cambridge Crystallographic Data Centre. Powder X-ray diffraction was performed on a D8 Advance diffractometer from Bruker.

### 2.4. Thermogravimetric analysis (TGA)

A ~~Perkin Elmer TGA7 instrument~~ [TGA Q500 from TA Instruments](#) was used for TGA under a nitrogen flow of 40 mL·min<sup>-1</sup> at atmospheric pressure. A total of [10 mg of \*\*1\*\*](#), 4 mg of **2** and 8 mg of **3** was placed on a platinum crucible, and measurements were performed in the temperature range 25-1000 °C at a heating rate of [40-20](#) °C min<sup>-1</sup>.

### 2.5. [Vibrational and](#) Optical spectroscopy measurements

[Fourier-transform infrared spectroscopy \(FT-IR\) was performed on KBr pellets and collected with a Bruker Equinox 55 FT-IR spectrometer.](#) Reflectance spectroscopy measurements were performed under sample direct illumination in a dual-beam spectrophotometer (Agilent Technologies Cary 5000 UV-Vis-NIR) equipped with a diffuse reflectance integration sphere.

## 3. Results and Discussions


Mis en forme : Police :Gras

### 3.1. Synthesis

Compounds **1**, **2** and **3** were obtained by combining Yb<sup>III</sup>, Er<sup>III</sup> and Eu<sup>III</sup> salts with both organic linkers ClCNAn<sup>2-</sup> and F<sub>4</sub>BDC<sup>2-</sup> under hydrothermal conditions. This method allowed to directly isolate the 3D coordination polymers as single crystals suitable for X-ray analysis. The purity of the polycrystalline samples was confirmed by FT-IR (Figure S1) and powder X-ray diffraction (Figures S4S2-S4). It should be noted that in our previous studies [44–45], one-pot room-temperature synthesis or layering techniques were used using the same precursor reagents and resulted in 2D coordination polymers. It thus highlights the influence of solvothermal conditions for the crystallization of 3D structures.


### 3.2. Crystal structures of [Yb<sub>2</sub>(μ-ClCNAn)<sub>2</sub>(μ-F<sub>4</sub>BDC)(H<sub>2</sub>O)<sub>4</sub>](H<sub>2</sub>O)<sub>3</sub> (**1**) and [Er<sub>2</sub>(μ-ClCNAn)<sub>2</sub>(μ-F<sub>4</sub>BDC)(H<sub>2</sub>O)<sub>4</sub>](H<sub>2</sub>O)<sub>4</sub> (**2**)

Compounds **1** and **2** crystallized in the triclinic space group *P*-1 and are isostructural. The asymmetric units contain one independent metal ion, two half chlorocyananilate (ClCNAn<sup>2-</sup>) ligands, one half tetrafluoroterephthalate (F<sub>4</sub>BDC<sup>2-</sup>) ligand and two coordinated water molecules (Figure 1). The Yb or Er metal ion is linked to four O atoms from ClCNAn<sup>2-</sup> bridging ligands, two O atoms from F<sub>4</sub>BDC<sup>2-</sup> and two O atoms from water molecules. Therefore, the metal ion is eight-coordinated within a strongly distorted trigonal prism geometry (*C*<sub>2v</sub> local symmetry) as shown by CShM values of 1.151 and 1.174 for Yb and Er respectively (Figure S2S5) [47]. The ClCNAn<sup>2-</sup> ligand coordinates two metal ions in a bis-bidentate mode, while the F<sub>4</sub>BDC<sup>2-</sup> ligand coordinates four metal ions in a tetradentate mode. As a consequence of this coordination mode, one-dimensional (1D) chains of Ln(III) connected by carboxylate groups are formed along the crystallographic *a* axis and show short metal-metal distances (Yb⋯Yb distance of 5.07 Å, Er⋯Er distance of 5.11 Å). These chains are separated by the anilate and F<sub>4</sub>BDC<sup>2-</sup> ligands with shortest distances between metal ions of 8.64 and 9.69 Å for Yb and 8.68 and 9.69 for Er (Figure S3S6).

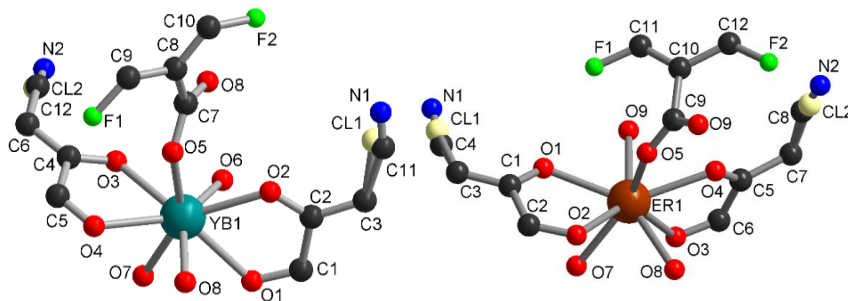


**Figure 1.** Asymmetric unit in **1** (left) and **2** (right).

**1** can also be described as two-dimensional (2D) metal-anilate layers running along the (0-11) lattice plane and connected together by the F<sub>4</sub>BDC<sup>2-</sup> ligands. Indeed, the two ClCNAn<sup>2-</sup> ligands are *trans* on the polyhedron, leading to an Ln(III)-ClCNAn<sup>2-</sup> 1D chain (Figure 2). These 1D chains are connected to each other by the first bidentate carboxylate group from the F<sub>4</sub>BDC<sup>2-</sup> ligand to form 2D layers. Finally, with the coordination of the second carboxylate group, the F<sub>4</sub>BDC<sup>2-</sup> ligand is able to bridge the layers and form the 3D architecture (Figure 2 and S4S7). Along the *a* axis, extended rectangular cavities are formed by the 1D anilate-based chains connected together by F<sub>4</sub>BDC<sup>2-</sup> spacers affording a 3D MOF (Figure 3). The accessible voids are calculated at 128 Å<sup>3</sup> per cell (and per formula unit) in **1** and 153 Å<sup>3</sup> in **2**. These cavities are filled with water solvent molecules (three per formula unit in **1** and four per formula unit in **2** according to the SQUEEZE procedure).

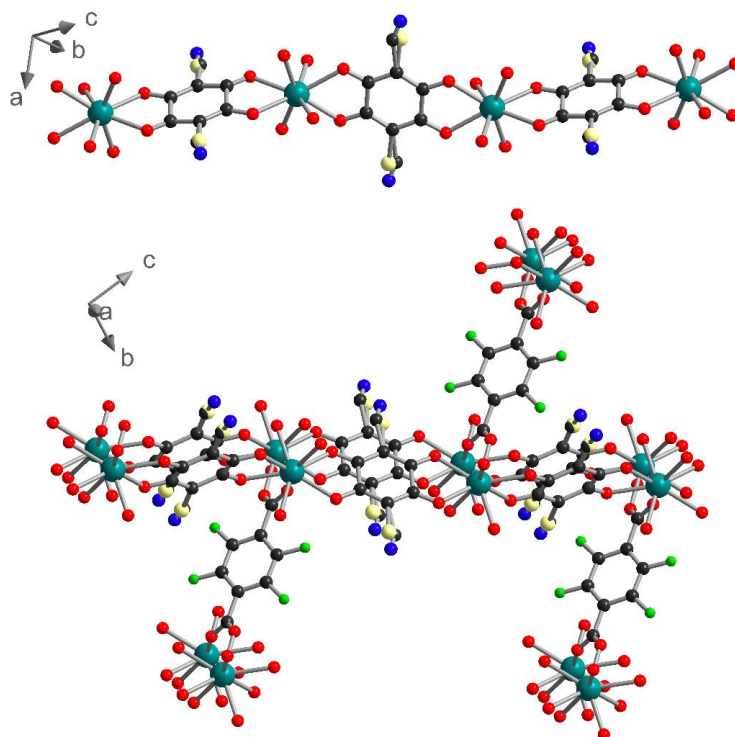

168  
169  
170  
171  
**Figure 2.** 1D chain of Yb-CICNAn<sup>2</sup> (top) and 3D network made by the connection of 1D chains with F<sub>4</sub>BDC<sup>2-</sup> ligands (bottom) in **1**. Color code: C (black), O (red), N (blue), F (green), Cl (light yellow), Yb (teal).

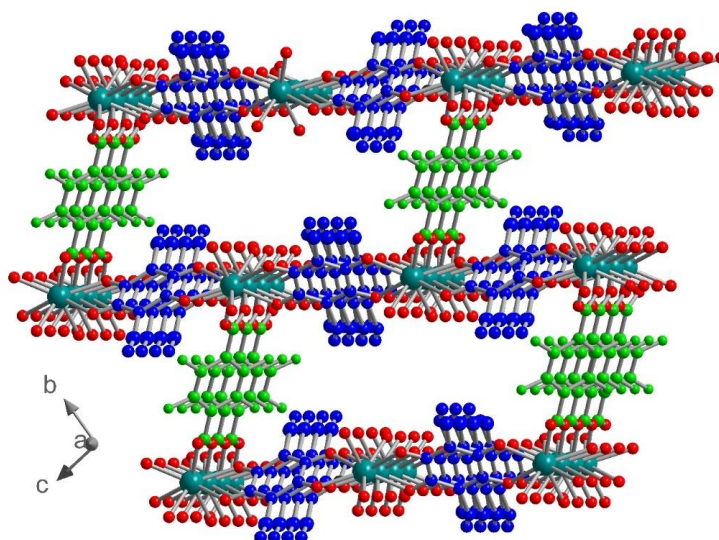

172  
173  
174  
**Figure 3.** View of the crystal structure in **1** showing the rectangular cavities along the *a* axis. CICNAn<sup>2</sup> and F<sub>4</sub>BDC<sup>2-</sup> are highlighted in blue and green respectively.

### 3.3. Crystal structure of $[Eu_2(\mu\text{-CICNAn})_2(\mu\text{-F}_4\text{BDC})(\text{H}_2\text{O})_6]$ (**3**)

Compound **3** crystallized in the monoclinic space group  $I2/a$ . The asymmetric unit contains one independent metal ion, two half CICNAn<sup>2-</sup> ligands, one-half F<sub>4</sub>BDC<sup>2-</sup> ligand and three water molecules (Figure 4). The Eu metal ion is linked to four O atoms from CICNAn<sup>2-</sup>, two O atoms from F<sub>4</sub>BDC<sup>2-</sup> and three O atoms from water molecules. Therefore, the Eu metal ion is nine-coordinated within a strongly distorted tricapped trigonal prism geometry ( $D_{3h}$  local symmetry) toward a capped square antiprism ( $C_{4v}$ ), with CShM values of 0.948 and 1.074 respectively. The metal ion is surrounded by two CICNAn<sup>2-</sup> ligands on opposite sides of the polyhedron and two adjacent F<sub>4</sub>BDC<sup>2-</sup> ligands, while the three water molecules are organized in a *fac* manner (Figure S2S5). The bridging ligands present the same coordination mode as in **1** and **2** (bis-bidentate and tetradentate modes for CICNAn<sup>2-</sup> and F<sub>4</sub>BDC<sup>2-</sup>, respectively). Therefore the crystal structure can also be described as Eu-CICNAn<sup>2-</sup> 1D chains connected to each other by F<sub>4</sub>BDC<sup>2-</sup> ligands leading to a 3D network (Figures 5 and 6). The carboxylate bridges lead to the shortest Eu...Eu distances of 5.56 Å, while the CICNAn<sup>2-</sup> linkers lead to distances between metal ions of 8.76 and 8.90 Å. In addition, a short Eu...Eu distance of 6.30 Å can be observed between two non-bridged metal ions (Figure S5S8).

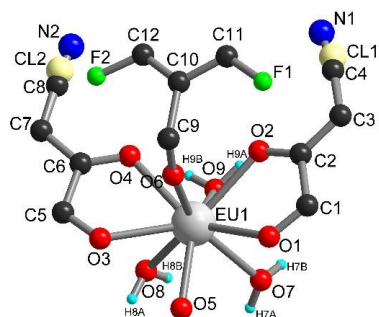


Figure 4. Asymmetric unit in **3**.


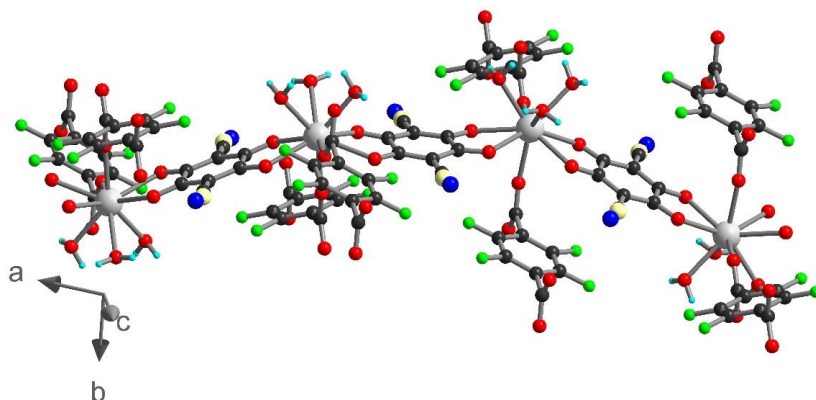


Figure 5. 1D chain of Eu-CICNAn<sup>2-</sup> connected by F<sub>4</sub>BDC<sup>2-</sup> ligands in **3**. Color code: C (black), H (cyan), O (red), N (blue), F (green), Cl (light yellow), Eu (grey).



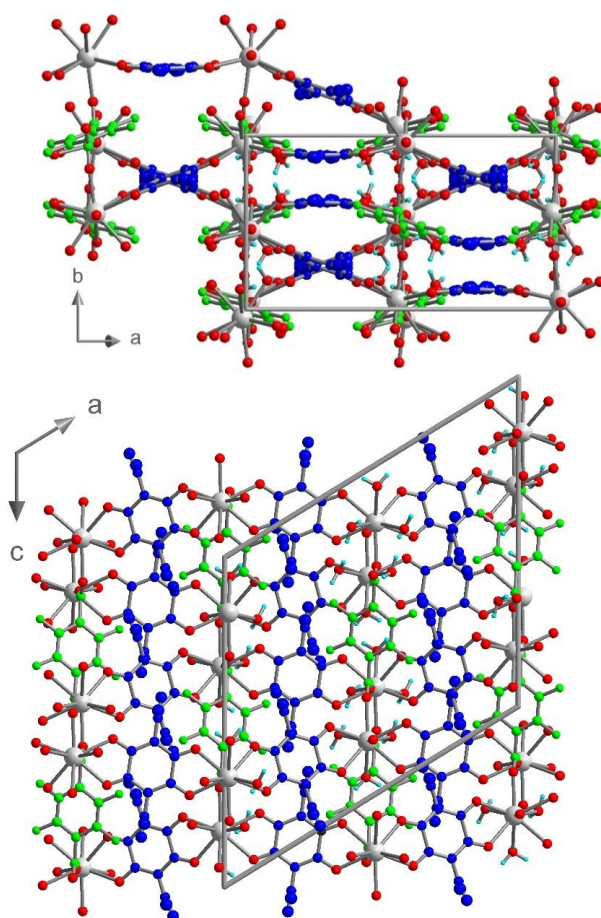


**Figure 6.** View of the crystal structure of **3** in the *ab* plane (top) and in the *ac* plane (bottom). C1CNAn<sup>2</sup> and F<sub>4</sub>BDC<sup>2-</sup> are highlighted in blue and green respectively.

Although the three crystal structures share many features such as the metal to ligands stoichiometry (Ln/C1CNAn<sup>2</sup>/F<sub>4</sub>BDC<sup>2-</sup> ratio of 2/2/1) and the coordination mode of the ligands, the resulting 3D networks present very different topologies. This first origins from the size and coordination number of the metal ion (eight-coordinated for Yb/Er, nine-coordinated for Eu). As a result, the two adjacent F<sub>4</sub>BDC<sup>2-</sup> ligands from the same polyhedron lie parallel to each other in **1** and **2**, while they are oriented in opposite directions in the Eu compound (Figures 7 and S2S5). Moreover, in **1** and **2** linear Ln(III)-carboxylate chains run along the *a* direction, while in **3** the Ln(III) ions are not eclipsed along the 1D chains (Figure 7). Therefore, in **1** and **2** all Ln(III)-anilate 1D chains lie in the (0-11) lattice plane and the F<sub>4</sub>BDC<sup>2-</sup> in the (011) plane, leading to the formation of extended rectangular cavities along the *a* axis which are filled with water solvent molecules (Figure S6S9). In addition, in **3** one of the two independent half-anilate ligands presents a distortion which can be highlighted by a non-negligible dihedral angle of around 11° between the plane made by the C and O atoms from the ligand and the plane made by the Ln(III) metal centre and coordinated O atoms (Figure S7S10). On the other hand, the second half-anilate ligand is almost coplanar to the Ln(III) metal centres. This results in the strong curvature of the extended Ln(III)-anilate layer. Consequently, **3** is a



coordination polymer showing a more complex topology with the absence of apparent cavities and crystallization solvent molecules.

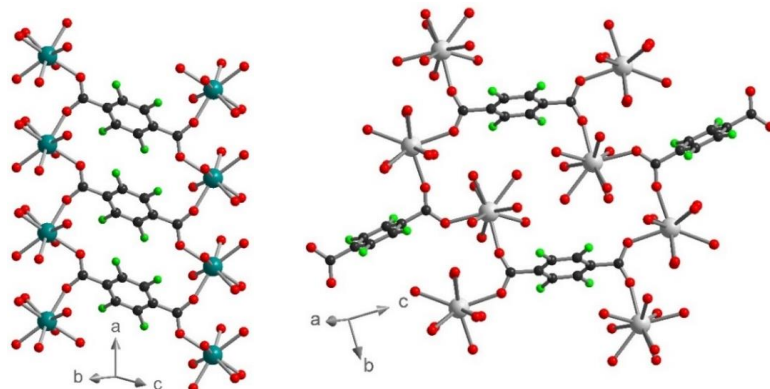

**Figure 7.** Coordination mode and orientation of the F<sub>4</sub>BDC<sup>2-</sup> ligands in **1** (left) and **3** (right). Color code: C (black), O (red), F (green), Yb (teal), Eu (grey).

#### 3.4. Thermogravimetric analysis (TGA)

TGA was performed on polycrystalline samples of **1**, **2** and **3** (Figure S8S11). The main difference between both compounds is the first loss of weight (about 4 and 6%) in **1** and **2**, corresponding to the loss of between three and four water solvent molecules, in agreement with the number of water molecules calculated in the cavities of the MOF structures. In **3**, such loss was not observed below 100 °C. Between 100 and 300 °C, **1** and **2** shows a gradual an additional loss of about 6–7% of weight, which may correspond to the loss of four coordinated water molecules. However in **3**, the 5% weight loss may correspond to only three over the six coordinated water molecules. Above 375 °C, both the three compounds present an important weight loss, although more gradual in **1** and **2**, which is attributed to the 3D networks collapse.

#### 3.5. Optical characterization

The Diffuse Reflectance (DR) spectra spanning through the UV-Vis-NIR spectral range show evidence of both ClCNAn<sup>2-</sup> ligand and Yb/Er presence (Figure 8). The absorption onset of ClCNAn<sup>2-</sup> is clearly visible below 650 nm in all compounds. At longer wavelengths, the spectra are dominated by Yb(III) and Er(III) absorption transitions (979 nm for Yb(III), 1510, 971 and 790 nm for Er(III)) [44–45]. On the other hand, absorption transitions associated to Eu(III) are not visible due to the overlap with those of ClCNAn<sup>2-</sup> organic linker. The band at ~1450 nm in **1** and **2** and dips observed between 1600 and 1800 nm in **3** were assigned to water absorption (this vibration is a combination of symmetrical and antisymmetrical stretchings of the coordinated water molecule) [45–48].

Mis en forme : Police :Gras

Mis en forme : Police :Gras

Mis en forme : Police :Gras

Mis en forme : Police :Gras

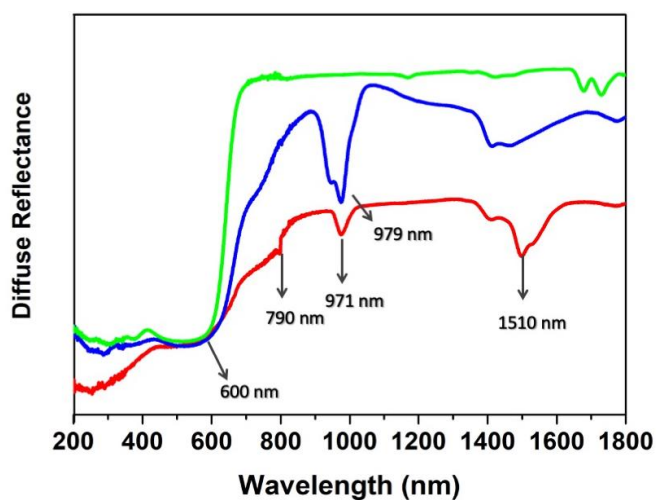


Figure 8. Optical characterization of crystals of 1 (blue line), 2 (red line) and 3 (green line).

#### 4. Discussion/Conclusions

Using the heteroleptic strategy, we have been able to prepare and structurally characterize 3D coordination polymers based on Ln(III) ions and anilate/terephthalate bridging ligands. Notably, the solvothermal synthetic protocol herein optimized seems to play a role in determining the higher dimensionality (3D) and MOF architectures of the materials, especially when compared with room-temperature one-pot synthesis, which has afforded 2D coordination polymers with the same bridging ligands and NIR-emitting lanthanides [44–45]. The resulting crystal structure is strongly affected by the nature of the Ln(III) ion. With Yb(III) and Er(III), the 3D architecture in 1 and 2 is based on Ln(III)-anilate 1D chains connected along the two adjacent directions by tetradentate terephthalate linkers and eclipsed along the *a* direction leading to an Ln-MOF with extended rectangular cavities and structural porosity. On the other hand, with the use of Eu, the 3D architecture of 3 is more complex because of the curvature observed in the Ln(III)-anilate 1D chains and of the many distinct positions of the terephthalate linkers around those chains. TGA confirmed the stability of the 3D network up to 375 °C and the presence of solvent water molecules in the MOF structure of 2. [Diffuse reflectance studies have shown to be a valuable probe to identify the presence of water in the inner coordination sphere of the Ln\(III\) ion.](#) [48] In the progress of this work, adsorption and luminescence properties of Yb(III), Er(III) and Nd(III) Ln-MOFs will be studied for application in sensing or molecular recognition in the NIR region. On the other hand, we are currently exploiting the use of different Ln(III) ions, as Dy(III) and Tb(III), to provide 3D networks with interesting magnetic properties such as ferro/ferrimagnetism and/or single-molecule-magnet behaviour.

**Supplementary Materials:** The following supporting information can be downloaded at: [www.mdpi.com/xxx/s1](http://www.mdpi.com/xxx/s1), Figure S1: [FT-IR spectra of KHClCNAn, H<sub>2</sub>F<sub>4</sub>BDC, 1, 2 and 3 in the 2000–700 cm<sup>-1</sup> region](#); [Figures S2–S4](#): Simulated (black) and experimental (blue) X-ray powder patterns of 1 (S2), 2 (S3) and 3 (S4); [Figure S2S5](#): Coordination environment of the metal ion in 1 and 3; [Figure S3S6](#): View of the crystal structures of 1 and 2 in the *ac* plane highlighting the shortest Ln(III)–Ln(III) distances; [Figure S4S7](#): Views of the extended structure in 1; [Figure S5S8](#): View of the crystal structure of 3 highlighting the shortest Eu...Eu distances; [Figure S6S9](#): View of the crystal structure of 1 highlighting the (011) and (0-11) lattice planes; [Figure S7S10](#): View of the Eu-anilate 1D chain of 3 highlighting the plane of the ligand (in blue) and the plane made by the Ln metal centre and the two coordinated O atoms (in red); [Figure S8S11](#): TGA of compounds 1, 2 and 3.

Mis en forme : Indice

Mis en forme : Indice

Mis en forme : Police :Gras

Mis en forme : Police :Gras

Mis en forme : Police :Gras

Mis en forme : Exposant

Mis en forme : Police :Gras

Mis en forme : Police :Gras

Mis en forme : Police :Gras

**Author Contributions:** Conceptualization, N.A., A.A. and M.L.M.; Synthesis, M.O., F.M. and S.A.S.; Structural characterization, F.M. and A.A.; Optical characterization, M.O.; Writing, A.A. and M.L.M.; Review & editing, all authors. All authors have read and agreed to the published version of the manuscript.

**Funding:** This research was funded in Italy by the Fondazione di Sardegna, Convenzione triennale tra la Fondazione di Sardegna e gli Atenei Sardi, Regione Sardegna, L.R. 7/2007 annualità ~~2016~~2018, ~~DGR 28/21 del 17.05.2015,~~ through Projects F74I19000940007 and F74I19000920007 for the post-doctoral fellowship of MO. MIUR (Ministry of Education, University, Research) UNICA-UNISS Consortium PhD Course on Chemical Sciences and Technologies is also acknowledged for the PhD grant of FM. CESA (Centro d' Eccellenza per la Sostenibilita' Ambientale, accordo di programma RAS-UNICA-IGEA-AUSI, project number E58C16000080003) is acknowledged for the PhD grant of MO. The work in France was supported by the CNRS, the University of Angers, and the RFI LUMOMAT network (ASCO MMM project).

**Data Availability Statement:** The data presented in this study are available on request from the corresponding authors.

~~**Acknowledgments:** In this section, you can acknowledge any support given which is not covered by the author contribution or funding sections. This may include administrative and technical support, or donations in kind (e.g., materials used for experiments).~~

**Conflicts of Interest:** The authors declare no conflict of interest.

## References

1. Batten, S. R.; Champness, N. R.; Chen, X.-M.; Garcia-Martinez, J.; Kitagawa, S.; Öhrström, L.; O'Keeffe, M.; Pail Suh, M.; Reedijk, J. Coordination polymers, metal-organic frameworks and the need for terminology guidelines. *CrystEngComm* **2012**, *14*, 3001-3004.
2. De Lill, D. T.; Cahill, C. L. Coordination Polymers of the Lanthanide Elements: A Structural Survey. *Progr. Inorg. Chem.* **2007**, *55*, 143-204.
3. S. L. James. Metal-organic frameworks. *Chem. Soc. Rev.* **2003**, *32*, 276-288.
4. Saines, P. J.; Bristowe, N. C. Probing magnetic interactions in metal-organic frameworks and coordination polymers microscopically. *Dalton Trans.* **2018**, *47*, 13257-13280.
5. Gorai, T.; Schmitt, W.; Gunnlaugsson, T. Highlights of the development and application of luminescent lanthanide based coordination polymers, MOFs and functional nanomaterials. *Dalton Trans.* **2021**, *50*, 770-784.
6. Decadt, R.; Van Hecke, K.; Depla, D.; Leus, K.; Weinberger, D.; Van Driessche, I.; Van Der Voort, P.; Van Deun, R. Synthesis, Crystal Structures, and Luminescence Properties of Carboxylate Based Rare-Earth Coordination Polymers. *Inorg. Chem.* **2012**, *51*, 11623-11634.
7. Hirai, Y.; Nakanishi, T.; Kitagawa, Y.; Fushimi, K.; Seki, T.; Ito, H.; Hasegawa, Y. Triboluminescence of Lanthanide Coordination Polymers with Face-to-Face Arranged Substituents. *Angew. Chem. Int. Ed.* **2017**, *56*, 7171-7175.
8. Du, P.-Y.; Li, H.; Fu, X.; Gu, W.; Liu, X. A 1D anionic lanthanide coordination polymer as an adsorbent material for the selective uptake of cationic dyes from aqueous solutions. *Dalton Trans.* **2015**, *44*, 13752-13759.
9. Zeng, H.-H.; Qiu, W.-B.; Zhang, L.; Liang, R.-P.; Qiu, J.-D. Lanthanide Coordination Polymer Nanoparticles as an Excellent Artificial Peroxidase for Hydrogen Peroxide Detection. *Anal. Chem.* **2016**, *88*, 6342-6348.
10. Chen, H.-J.; Chen, L.-Q.; Lin, L.-R.; Long, L.-S.; Zheng, L.-S. Doped Luminescent Lanthanide Coordination Polymers Exhibiting both White-Light Emission and Thermal Sensitivity. *Inorg. Chem.* **2021**, *60*, 6986-6990.
11. Islam, M. J.; Kitagawa, Y.; Tsurui, M.; Hasegawa, Y. Strong circularly polarized luminescence of mixed lanthanide coordination polymers with control of 4f electronic structures. *Dalton Trans.* **2021**, *50*, 5433-5436.
12. Benmansour, S.; Pérez-Herráez, I.; López-Martínez, G.; Gómez-García, C. J. Solvent-modulated structures in anilato-based 2D coordination polymers. *Polyhedron* **2017**, *135*, 17-25.
13. Zheng, Z.; Lu, H.; Wang, Y.; Bao, H.; Li, Z.-J.; Xiao, G.-P.; Lin, J.; Qian, Y.; Wang, J.-Q. Tuning of the Network Dimensionality and Photoluminescent Properties in Homo- and Heteroleptic Lanthanide Coordination Polymers. *Inorg. Chem.* **2021**, *60*, 1359-1366.
14. Benmansour, S.; Gómez-García, C. J.; Hernández-Paredes, A. The Complete Series of Lanthanoid-Chloranilato Lattices with Dimethylsulfoxide: Role of the Lanthanoid Size on the Coordination Number and Crystal Structure. *Crystals* **2022**, *12*, 261.
15. Fourcade-Cavillou, F.; Trombe, J.-C. Synthesis and crystal structure of  $\text{La}(\text{H}_2\text{O})(\text{C}_2\text{O}_4)_2(\text{CN}_3\text{H}_6)$  and of  $[\text{Nd}(\text{H}_2\text{O})_2(\text{C}_2\text{O}_4)_2(\text{NH}_4)(\text{CN}_3\text{H}_6)]$ . *Solid State Sci.* **2002**, *4*, 1199-1208.
16. Li, Z.-Y.; Zhai, B.; Li, S.-Z.; Cao, G.-X.; Zhang, F.-Q.; Zhang, X.-F.; Zhang, F.-L.; Zhang, C. Two Series of Lanthanide Coordination Polymers with 2-Methylenesuccinate: Magnetic Refrigerant, Slow Magnetic Relaxation, and Luminescence Properties. *Cryst. Growth Des.* **2016**, *16*, 4574-4581.
17. Legendziewicz, J.; Keller, B.; Turowska-Tyrk, I.; Wojciechowski, W. Synthesis, optical and magnetic properties of homo- and heteronuclear systems and glasses containing them. *New J. Chem.* **1999**, *23*, 1097-1103.
18. Huskowska, E.; Glowiak, T.; Legendziewicz, J.; Oremek, G. Luminescence and crystal structure of neodymium and europium squarate hydrates. *J. Alloys Compd.* **1992**, *179*, 13-25.
19. Takano, R.; Ishida, T. Polymeric Terbium(III) Squarate Hydrate as a Luminescent Magnet. *Crystals* **2021**, *11*, 1221.
20. Reineke, T. M.; Eddaoudi, M.; Fehr, M.; Kelley, D.; Yaghi, O. M. From Condensed Lanthanide Coordination Solids to Microporous Frameworks Having Accessible Metal Sites. *J. Am. Chem. Soc.* **1999**, *121*, 1651-1657.
21. Daiguebonne, C.; Gérault, Y.; Guillou, O.; Lecerf, A.; Boubekeur, K.; Batail, P.; Kahn, M.; Kahn, O. A new honeycomb-like molecular compound:  $\text{Gd}[\text{C}_6\text{H}_3(\text{COO})_3](\text{H}_2\text{O})_3 \cdot 1.5\text{H}_2\text{O}$ . *J. Alloys Compd.* **1998**, *275*, 50-53.
22. Wang, S.-J.; Tian, Y.-W.; You, L.-X.; Ding, F.; Meert, K. W.; Poelman, D.; Smet, P. F.; Ren, B.-Y.; Sun, Y.-G. Solvent-regulated assemblies of 1D lanthanide coordination polymers with the tricarboxylate ligand. *Dalton Trans.* **2014**, *43*, 3462-3470.
23. Mathis II, S. R.; Golafale, S. T.; Solntsev, K. M.; Ingram, C. W. Anthracene-Based Lanthanide Metal-Organic Frameworks: Synthesis, Structure, Photoluminescence, and Radioluminescence Properties. *Crystals* **2018**, *8*, 53.
24. You, L.-X.; Cao, S.-Y.; Guo, Y.; Wang, S.-J.; Xiong, G.; Dragutan, I.; Dragutan, V.; Ding, F.; Sun, Y.-G. Structural insights into new luminescent 2D lanthanide coordination polymers using an N, N' -disubstituted benzimidazole zwitterion. Influence of the ligand. *Inorg. Chim. Acta* **2021**, *525*, 120441.
25. Wu, Y.; Zhou, Y.; Cao, S.; Cen, P.; Zhang, Y.-Q.; Yang, J.; Liu, X. Lanthanide Metal-Organic Frameworks Assembled from Unexplored Imidazolylcarboxylic Acid: Structure and Field-Induced Two-Step Magnetic Relaxation. *Inorg. Chem.* **2020**, *59*, 11930-11934.
26. Wang, Z.-X.; Wu, Q.-F.; Liu, H.-J.; Shao, M.; Xiao, H.-P.; Li, M.-X. 2D and 3D lanthanide coordination polymers constructed from benzimidazole-5,6-dicarboxylic acid and sulfate bridged secondary building units. *CrystEngComm* **2010**, *12*, 1139-1146.

- 356 27. Chen, Y.; Zhao, X.; Gao, R.; Ruan, Z.; Lin, J.; Liu, S.; Tian, Z.; Chen, X. Temperature-induced solvent assisted single-crystal-to-single-crystal transformation of Mg(II)-Ln(III) heterometallic coordination polymers. *J. Solid State Chem.* **2020**, *292*, 121674.
- 359 28. García-García, A.; Zabala-Lekuona, A.; Goñi-Cárdenas, A.; Cepeda, J.; Seco, J. M.; Salinas-Castillo, A.; Choquesillo-Lazarte, D.; Rodríguez-Diéguez, A. Magnetic and Luminescent Properties of Isostructural 2D Coordination Polymers Based on 2-Pyrimidinecarboxylate and Lanthanide Ions. *Crystals* **2020**, *10*, 571.
- 361 29. Abhervé, A.; Mañas-Valero, S.; Clemente-León, M.; Coronado, E. Graphene related magnetic materials: micromechanical exfoliation of 2D layered magnets based on bimetallic anilate complexes with inserted  $[\text{Fe}^{\text{III}}(\text{acac}-\text{trien})]^+$  and  $[\text{Fe}^{\text{III}}(\text{sal}-\text{trien})]^+$  molecules. *Chem. Sci.* **2015**, *6*, 4665-4673.
- 362 30. Ashoka Sahadevan, S.; Abhervé, A.; Monni, N.; Sáenz de Pipaón, C.; Galán-Mascarós, J. R.; Waerenborgh, J. C.; Vieira, B. J. C.; Auban-Senzier, P.; Pillet, S.; Bendeif, E.; Alemany, P.; Canadell, E.; Mercuri, M. L.; Avarvari, N. Conducting Anilate-Based Mixed-Valence Fe(II)Fe(III) Coordination Polymer: Small-Polaron Hopping Model for Oxalate-Type Fe(II)Fe(III) 2D Networks. *J. Am. Chem. Soc.* **2018**, *140*, 12611-12621.
- 365 31. Benmansour, S.; Gómez-García, C. J. Lanthanoid-Anilato Complexes and Lattices. *Magnetochemistry* **2020**, *6*, 71.
- 369 32. Ashoka Sahadevan, S.; Monni, N.; Abhervé, A.; Marongiu, D.; Sarritzu, V.; Sestu, N.; Saba, M.; Mura, A.; Bongiovanni, G.; Cannas, C.; Quochi, F.; Avarvari, N.; Mercuri, M. L. Nanosheets of Two-Dimensional Neutral Coordination Polymers Based on Near-Infrared-Emitting Lanthanides and a Chlorocyanilate Ligand. *Chem. Mater.* **2018**, *30*, 6575-6586.
- 370 33. Benmansour, S.; Hernández-Paredes, A.; Bayona-Andrés, M.; Gómez-García, C. J. Slow Relaxation of the Magnetization in Anilato-Based Dy(III) 2D Lattices. *Molecules* **2021**, *26*, 1190.
- 371 34. Abrahams, B. F.; Hudson, T. A.; McCormick, L. J.; Robson, R. Coordination Polymers of 2,5-Dihydroxybenzoquinone and Chloranilic Acid with the (10,3)-*a* Topology. *Cryst. Growth Des.* **2011**, *11*, 2717-2720.
- 372 35. Darago, L. E.; Aubrey, M. L.; Yu, C. J.; Gonzales, M. I.; Long, J. R. Electronic Conductivity, Ferrimagnetic Ordering, and Reductive Insertion Mediated by Organic Mixed-Valence in a Ferric Semiquinoid Metal-Organic Framework. *J. Am. Chem. Soc.* **2015**, *137*, 15703-15711.
- 373 36. Monni, N.; Andres-Garcia, E.; Caamaño, K.; García-López, V.; Clemente-Juan, J. M.; Giménez-Marqués, M.; Oggianu, M.; Cadoni, E.; Mínguez Espallargas, G.; Clemente-León, M.; Mercuri, M. L.; Coronado, E. A thermally/chemically robust and easily regenerable anilato-based ultramicroporous 3D MOF for CO<sub>2</sub> uptake and separation. *J. Mater. Chem. A* **2021**, *9*, 25189-25195.
- 374 37. Abrahams, B. F.; Coleiro, J.; Ha, K.; Hoskins, B. F.; Orchard, S. D.; Robson, R. Dihydroxybenzoquinone and Chloranilic Acid Derivatives of Rare Earth Metals. *J. Chem. Soc. Dalton Trans.* **2002**, 1586-1594.
- 375 38. Bondaruk, K.; Hua, C. Effect of Counterions on the Formation and Structures of Ce(III) and Er(III) Chloranilate Frameworks. *Cryst. Growth Des.* **2019**, *19*, 3338-3347.
- 376 39. Wang, Y.; Liu, X.; Li, X.; Zhai, F.; Yan, S.; Liu, N.; Chai, Z.; Xu, Y.; Ouyang, X.; Wang, S. Direct Radiation Detection by a Semiconductive Metal-Organic Framework. *J. Am. Chem. Soc.* **2019**, *141*, 8030-8034.
- 377 40. Ashoka Sahadevan, S.; Monni, N.; Abhervé, A.; Cosquer, G.; Oggianu, M.; Ennas, G.; Yamashita, M.; Avarvari, N.; Mercuri, M. L. Dysprosium Chlorocyanilate-Based 2D-Layered Coordination Polymers. *Inorg. Chem.* **2019**, *58*, 13988-13998.
- 378 41. Huang, G.; Yang, P.; Wang, N.; Wu, J.-Z.; Yu, Y. First lanthanide coordination polymers with N,N-dimethylformamide hydrolysis induced formate ligands. *Inorg. Chim. Acta* **2012**, *384*, 333-339.
- 379 42. Seidel, C.; Lorbeer, C.; Cybińska, J.; Mudring, A.-V.; Ruschewitz, U. Lanthanide Coordination Polymers with Tetrafluoroterephthalate as a Bridging Ligand: Thermal and Optical Properties. *Inorg. Chem.* **2012**, *51*, 4679-4688.
- 380 43. Chen, B.; Yang, Y.; Zapata, F.; Qian, G.; Luo, Y.; Zhang, J.; Lobkovsky, E. B. Enhanced Near-Infrared-Luminescence in an Erbium Tetrafluoroterephthalate Framework. *Inorg. Chem.* **2006**, *45*, 8882-8886.
- 381 44. Ashoka Sahadevan, S.; Monni, N.; Oggianu, M.; Abhervé, A.; Marongiu, D.; Saba, M.; Mura, A.; Bongiovanni, G.; Mameli, V.; Cannas, C.; Avarvari, N.; Quochi, F.; Mercuri, M. L. Heteroleptic NIR-Emitting Yb(III)/Anilate-Based Neutral Coordination Polymer Nanosheets for Solvent Sensing. *ACS Appl. Nano Mater.* **2020**, *3*, 94-104.
- 382 45. Ashoka Sahadevan, S.; Manna, F.; Abhervé, A.; Oggianu, M.; Monni, N.; Mameli, V.; Marongiu, D.; Quochi, F.; Gendron, F.; Le Guennic, B.; Avarvari, N.; Mercuri, M. L. Combined Experimental/Theoretical Study on the Luminescent Properties of Homoleptic/Heteroleptic Erbium(III) Anilate-Based 2D Coordination Polymers. *Inorg. Chem.* **2021**, *60*, 17765-17774.
- 383 46. Atzori, M.; Artizzu, F.; Marchiò, L.; Loche, D.; Caneschi, A.; Serpe, A.; Deplano, P.; Avarvari, N.; Mercuri, M. L. Switching-on luminescence in anilate-based molecular materials. *Dalton Trans.* **2015**, *44*, 15786-15802.
- 384 47. Llunell, M.; Casanova, D.; Girera, J.; Alemany, P.; Alvarez, S. SHAPE, version 2.1; Universitat de Barcelona: Barcelona, Spain.
- 385 48. [Viscarra-Rossel, R. A.; McBratney, A. B.; Artizzu, F.; Deplano, P.; Marchiò, L.; Mercuri, M. L.; Pilia, L.; Serpe, A.; Quochi, F.; Orrù, R.; Cordella, F.; Saba, M.; Mura, A.; Bongiovanni, G. New Insights on Infrared Emitters Based on Er-quinolinolate Complexes: Synthesis, Characterization, Structural and Photophysical Properties. Laboratory evaluation of a proximal sensing technique for simultaneous measurement of soil clay and water content. \*Geoderma-Adv. Funct. Mater.\* \*\*1998\*\*, \*2007\*, 8517-19-392365-2376.](#)

Mis en forme : Français  
(France)